

AD-A073 433

MASSACHUSETTS INST OF TECH CAMBRIDGE  
STRESS-ASSISTED ISOTHERMAL MARTENSITIC TRANSFORMATION AND TRANS--ETC(U)  
AUG 79 G B OLSON, M COHEN  
N00014-76-C-0171  
TR-3


F/G 11/6

UNCLASSIFIED

/ OF /  
AD  
A073433




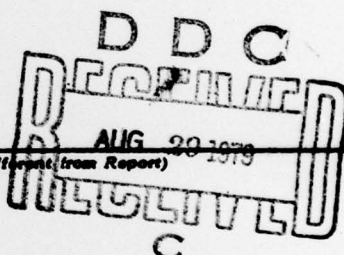
END  
DATE  
FILMED  
9-79  
DDC

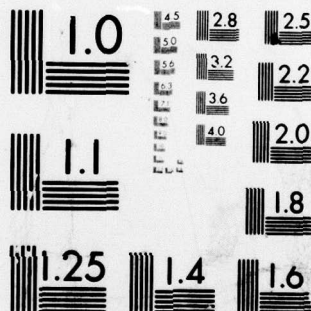

MICROCOPY RESOLUTION TEST CHART  
NATIONAL BUREAU OF STANDARDS-1963-A

## REPORT DOCUMENTATION PAGE

READ INSTRUCTIONS  
BEFORE COMPLETING FORM

1. REPORT NUMBER 3, 1979		2. GOVT ACCESSION NO.	3. RECIPIENT'S CATALOG NUMBER
4. TITLE (and Subtitle) "Stress-Assisted Isothermal Martensitic Transformation and Transformation Plasticity"		5. TYPE OF REPORT & PERIOD COVERED Technical; Oct. 1977 - Sept. 1979	
7. AUTHOR(s) Gregory B. Olson and Morris Cohen		6. PERFORMING ORG. REPORT NUMBER	
9. PERFORMING ORGANIZATION NAME AND ADDRESS Massachusetts Institute of Technology Cambridge, MA 02139		8. CONTRACT OR GRANT NUMBER(s) N00014-76-C-0171	
11. CONTROLLING OFFICE NAME AND ADDRESS Office of Naval Research Arlington, VA 22217		10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS	
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office)		12. REPORT DATE 2 August 1979	
<div style="text-align: center;">  </div>		13. NUMBER OF PAGES 6	
		15. SECURITY CLASS. (of this report) Unclassified	
16. DISTRIBUTION STATEMENT (of this Report) Unlimited			
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report) <div style="text-align: center;">  </div>			
18. SUPPLEMENTARY NOTES Presented at Joint U.S.-Japan Conference on "Mechanical Behavior of Metals and Alloys Associated with Displacive Phase Transformations," Troy, NY, June 12-15, 1979.			
19. KEY WORDS (Continue on reverse side if necessary and identify by block number) TRIP steels, martensitic transformation, transformation plasticity, stress-strain behavior, stress-assisted transformation.			
20. ABSTRACT (Continue on reverse side if necessary and identify by block number) Low-temperature plastic flow in TRIP steels has been found to be controlled by stress-assisted isothermal martensitic transformation. Under these conditions, theory of the transformation kinetics can be used to predict the temperature dependence of the flow stress, the shape of the stress-strain curve, and the dependence of flow properties on stress state.			

DD FORM 1473  
1 JAN 73EDITION OF 1 NOV 68 IS OBSOLETE  
S/N 0102-014-6601

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

AD A073433

DDC FILE COPY

⑥  
STRESS-ASSISTED ISOTHERMAL MARTENSITIC TRANSFORMATION  
AND TRANSFORMATION PLASTICITY.

⑩ G. B. Olson and Morris/Cohen

Massachusetts Institute of Technology

⑨ ⑪ TR-  
TECHNICAL REPORT NO. 3 1979

⑪  
2 August, 1979

⑫ 8p.

to

The Office of Naval Research

⑮  
Contract No. N00014-76-C-0171 NR031-795

Joint U.S.-Japan Conference on  
"Mechanical Behavior of Metals and Alloys Associated  
with Displacive Phase Transformations", Troy, N.Y.,  
June 12-15, 1979

Reproduction in whole or in part is permitted for any purpose  
of the United States Government.

79 08 27 118



STRESS-ASSISTED ISOTHERMAL MARTENSITIC TRANSFORMATION  
AND TRANSFORMATION PLASTICITY

G. B. Olson and Morris Cohen

Low-temperature plastic flow in TRIP steels has been found to be controlled by stress-assisted isothermal martensitic transformation. Under these conditions, theory of the transformation kinetics can be used to predict the temperature dependence of the flow stress, the shape of the stress-strain curve, and the dependence of flow properties on stress state.

I. Introduction

The true stress-strain plastic flow and transformation behavior of high-strength TRIP steels were recently measured during both uniform and localized flow as a function of temperature [1]. It was determined that the basic mode of transformation on cooling in these alloys is isothermal, and that the plastic flow at low temperatures is controlled by stress-assisted martensitic transformation. For these conditions, it is of interest to compare the observed transformation and flow behavior with that predicted from our knowledge of the kinetics of isothermal martensitic transformations.

II. Temperature Dependence of Transformation and Flow Behavior

The observed temperature dependence of the yield stress and the stress at which 1% martensite was detected [1] are shown in Fig. 1, indicating that transformation controls flow below the  $M_s^0$  temperature (maximum temperature at which transformation is induced by elastic stress). When plastic flow is controlled by stress-assisted isothermal transformation, yielding will occur at the stress for which the rate of transformation plasticity matches the imposed strain rate. Since the amount of transformation plasticity was found to be linearly related to the amount of transformation in this temperature region [1], this corresponds to a fixed rate of isothermal martensitic transformation.

The kinetics of isothermal martensitic transformations are known to be nucleation controlled with an activation energy that is linearly dependent on the transformation free-energy change,  $\Delta G$ . The transformation rate can then be expressed as [2]:

$$\dot{f} = n_s V v \exp\left(-\frac{A+B\Delta G}{RT}\right) \quad (1)$$

where  $f$  is the volume fraction martensite,  $n_s$  the density of nucleation sites,  $V$  the instantaneous mean martensitic plate volume,  $v$  the lattice vibration frequency,  $A$  and  $B$  are constants. The critical  $\Delta G$  for a fixed  $\dot{f}$  is then given by:

---

Massachusetts Institute of Technology, Cambridge, Massachusetts, U.S.A.

$$\Delta G_{\text{crit}}(\dot{f}) = -\frac{1}{B} \left( A + RT \ln \frac{\dot{f}}{n_s V_v} \right) \quad (2)$$

indicating a linear temperature dependence.

The transformation chemical free-energy change ( $\Delta G_{\text{ch}}$ ) vs. temperature for the alloy of Fig. 1, estimated from available thermodynamic parameters [3], is plotted in Fig. 2. Calculating the additional thermodynamic assist of the applied tensile stress [4], the total  $\Delta G$  at which transformation is observed for the low-temperature points in Fig. 1 is plotted to produce the  $\Delta G_{\text{crit}}$  curve of Fig. 2. The linear relation of eq. 2 is verified, and the parameters defined by the straight-line fit then predict the solid curve shown in Fig. 1 representing the stress  $\sigma_t$  required for a fixed rate of stress-assisted isothermal transformation. That transformation is observed below this stress for temperatures above  $M_s$  has been attributed [1] to the contribution of strain-induced nucleation defined as the production of new nucleation sites by plastic deformation.

The temperature sensitivity of the transformation kinetics in TRIP steels has been found to be a serious problem since heating effects encountered at moderate strain rates can cause a severe reduction in the uniform ductility associated with the deformation-induced transformation [5]. The temperature dependence of the stress-assisted transformation kinetics is zero at the minimum in the  $\sigma_t$  curve of Fig. 1 at

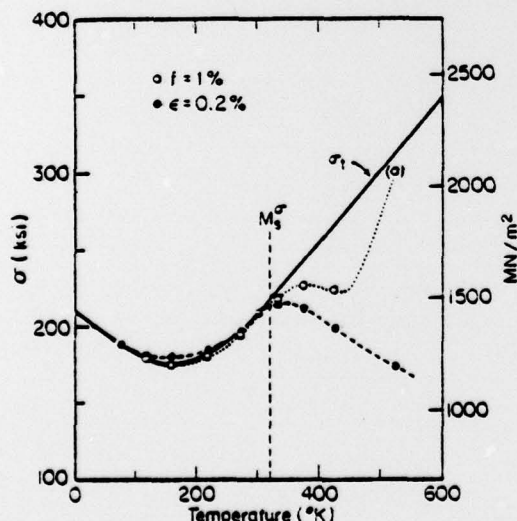


Fig. 1. Temperature dependence of stresses for plastic strain ( $\epsilon$ ) of 0.2% and for fraction martensite ( $f$ ) of 1% for Fe-9Cr-8Ni-4Mo-2Si-0.8Mn-0.27C TRIP steel (78% RA at 450°C) [1].

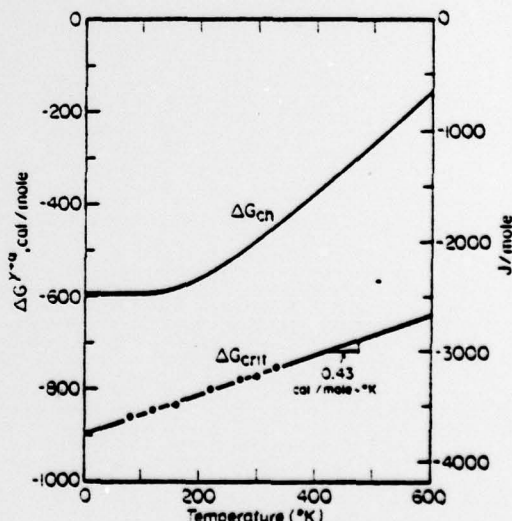


Fig. 2. Temperature dependence of transformation chemical free-energy change ( $\Delta G_{\text{ch}}$ ) and critical free-energy change ( $\Delta G_{\text{crit}}$ ) at which transformation is observed for alloy of Fig. 1.



~150°K. The temperature sensitivity of the contribution of stress-assisted nucleation to the overall transformation kinetics at ambient temperatures could thus be decreased by moving this minimum closer to 300°K. From Fig. 2 it can be seen that the  $\sigma_c$  minimum occurs when the slope of the  $\Delta G_{ch}(T)$  curve (controlled by the transformation entropy change,  $\Delta S_{ch}$ ) matches the slope of the  $\Delta G_{crit}(T)$  curve, corresponding to a value of 0.43 cal/mole°K (1.80 J/mole°K) for this alloy. Thermodynamic calculations suggest that substitution of manganese for nickel in these steels could bring the magnitude of the room-temperature transformation entropy change close to this value. In addition, isothermal transformation kinetic data [6] suggest that manganese may also alter the B parameter in eqs. 1 and 2 so as to favorably affect the slope of the  $\Delta G_{crit}(T)$  curve.

The temperature dependence of the yield stress for a high-manganese TRIP steel [7] is shown in Fig. 3. Although the as-warm-rolled material does not show a pronounced stress minimum, tempering at 570°C to lower the austenite stability by removing some carbon from solution indicates a minimum above 200°K. From the thermodynamic effect of carbon [3], this is expected to represent a lower limit to the actual temperature of the  $\sigma_c$  minimum when the carbon is in solution. It thus appears that manganese can alter the kinetics of the stress-assisted transformation in the desired way. It has also been predicted that manganese will favorably influence the temperature sensitivity of the strain-induced transformation kinetics [8]. Unfortunately, too high a manganese content is found to reduce ductility as measured by reduction in area [7].

### III. Isothermal Stress-Strain Curves

When plastic flow is controlled by stress-assisted transformation, our knowledge of the kinetics of isothermal martensitic transformations can also be used to predict the shape of the  $\sigma$ - $\epsilon$  curve. The course of isothermal transformation with time has been successfully modeled using eq. (1) with the number of nucleation sites per volume of sample,  $n_s$ , described by the relation [2,6]:

$$n_s = (n_i + pf - N_v)(1 - f) \quad \cdot(3)$$

where  $n_i$  is the initial density of sites,  $p$  is an "autocatalytic factor" accounting for new sites produced during transformation, and  $N_v$  is the number of martensitic plates per unit volume (accounting for sites which have already operated). The  $1-f$  factor takes into account potential sites which have been "swept up" by the transformation. Substituting eq. (3) in eq. (1) and incorporating an experimentally determined linear dependence of the overall average plate volume,  $\bar{V}$ , on  $N_v$ , a sigmoidal curve of volume fraction martensite,  $f$ , vs. time is predicted. The initial transformation rate is controlled by  $n_i$ , while the autocatalytic  $p$  factor can lead to upward curvature. Eventually the decreasing average plate volume can cause the rate of consumption of nuclei to exceed the rate of production, and a saturation level of transformation is reached. This model is found to accurately fit experimentally determined isothermal transformation curves at small amounts of transformation, but the approach to saturation of the calculated curves is somewhat too abrupt relative to the experimental observations [2, 6].

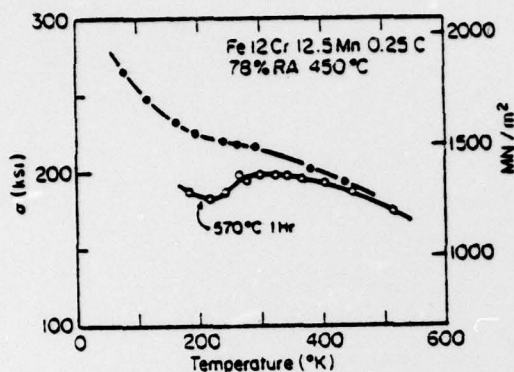


Fig. 3. Temperature dependence of yield stress of high-Mn TRIP steel in warm-rolled condition and after tempering [7].

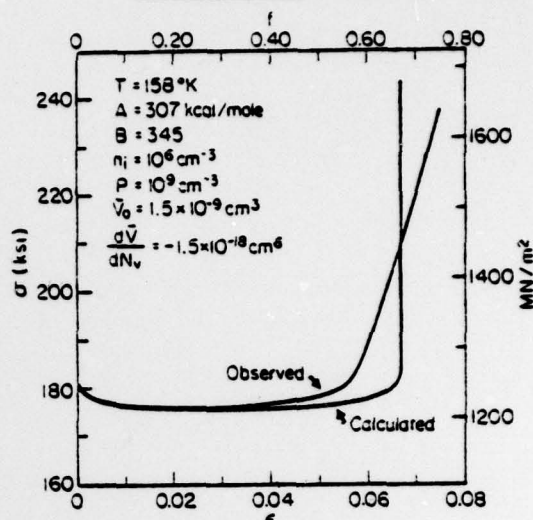


Fig. 4. Comparison of calculated and observed [1] true  $\sigma$ - $\epsilon$  curves for TRIP steel of Fig. 1.

Taking into account the thermodynamic effect of applied stress [4], this kinetic model can then express the stress required for a fixed rate of stress-assisted isothermal transformation as a function of the extent of transformation:

$$\sigma_{\epsilon}(f) = -\left(B \frac{d\Delta G}{d\sigma}\right)^{-1} \left[ A + B\Delta G_{ch} + RT \ln \frac{\dot{f}}{(n_i + pf - N_v)(1-f)V_v} \right]. \quad (4)$$

Given the experimentally observed linear relation between transformation plasticity and the extent of transformation [1], we can substitute the simple relation  $f = k\epsilon$ , with  $k$  a constant, and obtain a complete constitutive relation predicting the  $\sigma$ - $\epsilon$  behavior when plastic flow is controlled by stress-assisted isothermal martensitic transformation. As the last term in eq. (4) suggests, the yield stress will be controlled by  $n_i$ , but on further straining (transformation) the  $p$  factor can cause the denominator to increase with an attendant drop in stress. As a saturation level of transformation is approached, the denominator approaches zero and the stress must rise rapidly.

Equation (4) was fitted to the  $\sigma$ - $\epsilon$  curve measured at 158°K for the TRIP steel of Fig. 1 [1] using the  $A$  and  $B$  parameters determined from Fig. 2 and typical values [2,6] of the other kinetic parameters. Calculated and observed curves are compared in Fig. 4. The model accurately accounts for the initial stress drop that gives rise to Lüders band formation in these steels, but as expected, the approach to a saturation level, with the attendant high strain hardening, is too abrupt. We believe that this discrepancy is due to the assumption of a singly-activated process, and better agreement could be obtained for both the



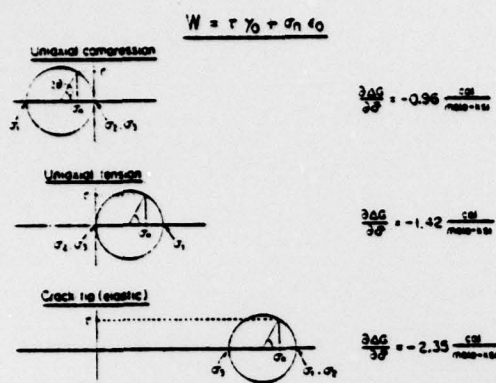


Fig. 5. Calculated work of resolved shear stress,  $\tau$ , and normal stress,  $\sigma_n$ , assisting transformation shape change with shear and normal strains,  $\gamma_0$  and  $\epsilon_0$ .

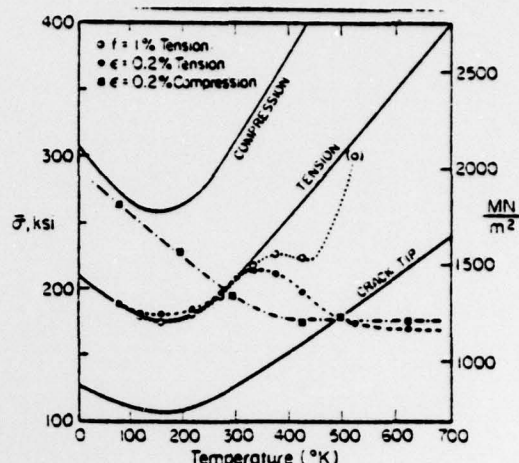


Fig. 6. Calculated transformation stresses and measured yield stresses for TRIP steel of Fig. 1 under different stress states.

conventional  $f$  vs.  $t$  data and the  $\sigma$ - $\epsilon$  curves by adopting a distribution of activation energies as indicated by the isothermal experiments of Magee [9].

#### IV. Influence of Stress State

Patel and Cohen [4] showed that, due to the transformation volume change, the work done by an applied stress assisting the shape change of a martensitic transformation (calculated for the most favorable plate orientation) will depend on the stress state. Figure 5 shows the relevant Mohr's circle diagrams and calculated values of  $\partial \Delta G / \partial \bar{\sigma}$  for various stress states (using equivalent stress,  $\bar{\sigma}$ ) based on the Patel and Cohen procedure. Using these values in eq. 4 we can predict the temperature dependence of the transformation stress,  $\sigma_t$ , for different stress states as indicated by the solid curves in Fig. 6. At temperatures where transformation controls flow, a large strength-differential (S-D) effect, comparing flow stress in tension and in compression, is expected. The measured yield stress in compression for the same alloy represented in Fig. 1 is also shown in Fig. 6 and compared with the tensile yield values.

Below  $300^{\circ}\text{K}$  the expected large S-D effect is observed. The curves suggest that flow is controlled by transformation in tension, but probably by slip in compression. Above  $500^{\circ}\text{K}$  where slip controls flow in both tension and compression, a normal S-D effect of a few percent is observed. However, in the region between  $300^{\circ}\text{K}$  and  $500^{\circ}\text{K}$  where slip is apparently still controlling flow, an anomalous negative S-D effect is observed in which the tensile yield strength is significantly higher

than the compressive yield. In thermodynamic terms, the comparison of flow stress for two stress states is equivalent to comparing alloys of differing thermodynamic stability, and this effect is therefore analogous to a similar observation by Breedis and Robertson [10] in measuring the critical resolved shear stress for slip in Fe-Cr-Ni crystals of different Ni contents. It has been suggested that such "pre-transformation strengthening" effects might arise from an influence of lattice metastability on dislocation mobility as the conditions for spontaneous dislocation dissociations related to martensitic nucleation are approached [11].

The calculated  $\sigma_c(T)$  curve for the stress state of an elastic crack tip is also shown in Fig. 6. It appears that transformation will control flow over a wider temperature range and cause a significant reduction in effective flow stress. Such an effect may be desirable from the standpoint of strength/toughness combinations, allowing a high uniaxial tensile strength to be achieved while retaining the crack tip plasticity of a much softer material.

#### V. Closure

The martensitic transformation represents a unique deformation mechanism in that its kinetics can be studied independently of applied stress and the information obtained then used to predict a variety of aspects of mechanical behavior. The potential exists for the achievement and control of rather unusual mechanical properties.

This work is supported by the Office of Naval Research under Contract No. N00014-76-C-0171, NR 031-795.

#### References

1. G. B. Olson and M. Azrin, Met. Trans. 9A (1978), 713.
2. S. R. Pati and M. Cohen, Acta Met. 17 (1969), 189.
3. L. Kaufman, ManLabs-NPL Thermochemical Databank, 1977.
4. J. R. Patel and M. Cohen, Acta Met. 1 (1953), 531.
5. M. Azrin, G. B. Olson, and R. A. Gagne, Mater. Sci. Eng. 23 (1976), 33.
6. V. Raghavan and M. Cohen, Met. Trans. 2 (1971), 2409.
7. G. B. Olson and M. Azrin, AMMRC unpublished research, 1977.
8. G. B. Olson and M. Cohen, Met. Trans. 6A (1975), 791.
9. C. L. Magee, Met. Trans. 2 (1971), 2419.
10. J. F. Breedis and W. D. Robertson, Acta Met. 11 (1963), 547.
11. G. B. Olson, Sc.D. Thesis, MIT Dept. Mat. Sci. and Eng., 1974, Appendix C.

Accession For	NTIS GDA&I			
	DDC TAB			
	Unannounced			
	Justification			
By				
Distribution/				
Availability Codes				
Avail and/or				
Dist special				
Dist				A